

Datasheet

Description:

AKROMID® B3 GK 50 natural (3690) is a 50% glass bead reinforced polyamide 6 with low warpage and high surface appearance and light inherent color

Applications

Housings and covers in the automotive, electro and furniture industry.

Typical values	Test specification	Method	Unit	Value d.a.m.
----------------	--------------------	--------	------	-----------------

Mechanical Properties

Tensile modulus	1 mm/min	ISO 527-2	MPa	5700
Stress at break	5 mm/min	ISO 527-2	MPa	75
Strain at break	5 mm/min	ISO 527-2	%	4
Flexural modulus	2 mm/min	ISO 178	MPa	5200
Flexural strength	2 mm/min	ISO 178	MPa	135
Charpy impact strength	23°C	ISO 179-1/1eU	kJ/m ²	42
Charpy impact strength	-30°C	ISO 179-1/1eU	kJ/m ²	32
Charpy notched impact strength	23°C	ISO 179-1/1eA	kJ/m ²	3
Charpy notched impact strength	-30°C	ISO 179-1/1eA	kJ/m ²	1

Electrical Properties

Volume resistivity		IEC 60093	Ohm x cm	1,0E+15
Surface resistivity		b.o. IEC 60093	Ohm	1,0E+13
Comparative tracking index	test solution A	IEC 60112		500

Thermal Properties

Melting temperature	DSC, 10K/min	DIN EN 11357-1	°C	225
Temp. of deflection under load HDT/A	1,8 MPa	ISO 75	°C	75
Temp. of deflection under load HDT/B	0,45 MPa	ISO 75	°C	188

Flammability

Wall thickness			mm	0,4	0,8	1,6	2,0	3,2
Flammability		UL 94	class			HB		
GWFI		IEC 60695-2-12	°C			650		
Burning rate (< 100 mm/min)	> 1 mm thickness	FMVSS 302				+		

General Properties

Density	23°C	ISO 1183	g/cm ³	1,54
Content reinforcement/Content Filler		ISO 1172	%	50
Humidity absorption	70°C, 62% r.h.	ISO 1110	%	1,5
Water absorption	23°C, saturated	ISO 62	%	4,7


Processing

Molding shrinkage	flow	ISO 294-4	%	1,0
Molding shrinkage	transverse	ISO 294-4	%	1,1

b.o.: based on

Continuation

Processing recommendations

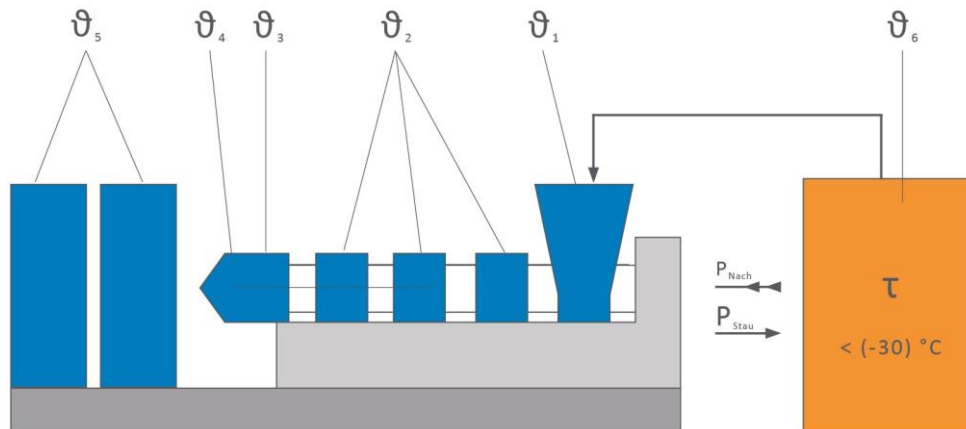

ϑ_6	Drying time	h	0 - 4
ϑ_6	Drying temperature	°C	80
	Processing moisture	%	0,02 - 0,1
ϑ_1	Feed section	°C	60 - 80
ϑ_2	Section 1 - Section 4	°C	240 - 290
ϑ_3	Nozzle	°C	260 - 300
ϑ_4	Melt	°C	270 - 290
ϑ_5	Mould	°C	80 - 100
P_{Nach}	Holding pressure, spec.	bar	300 - 800
P_{Stau}	Back pressure, spez.	bar	50 - 150
	Injection speed		medium to high
	Screw speed	m/min	8 - 15

The listed values are recommendations. Higher values should be used for higher glass loadings. We recommend only de-humidifying or vacuum dryers. Extensive drying can cause filling problems and surface defects.